

Optical Director Reorientation in NLCs Doped with Light-Absorbing Codendrimers of Different Generations

I. A. BUDAGOVSKY,¹ V. N. OCHKIN,¹
S. A. SHVETSOV,¹ M. P. SMAYEV,¹ A. S. ZOLOT'KO,¹
D. A. BRAZHNIKOV,¹ N. I. BOIKO,² AND
M. I. BARNIK³

¹Lebedev Physical Institute, Moscow, Russia

²Chemical Department, Moscow State University, Moscow, Russia

³Shubnikov Institute of Crystallography, Moscow, Russia

The orientational optical nonlinearity induced in NLCs by light-absorbing carbosilane codendrimers with statistical distribution of terminal aliphatic and azobenzene fragments has been studied comparatively for different (from the second to the fourth) codendrimer generations. It was found that all the codendrimers induce the negative nonlinearity (director rotates away from the light field thus decreasing the refractive index of the extraordinary wave). The orientational response increases with the generation number. The optical bistability is manifested for NLCs doped with the codendrimers of the second and third generations.

Keywords Dendrimers; light-induced Freedericksz transition; nematic liquid crystals; orientational nonlinearity

1. Introduction

The optical axis of nematic liquid crystals (NLCs) can be easily rotated by external influences, e.g., the light field [1–10]. Director rotation in pure (undoped) nematics occurs toward the light field and is due to force action on light-induced dipoles. The corresponding orientational optical nonlinearity is nine orders of magnitude larger than the Kerr nonlinearity of ordinary liquids [1,4].

Doping of the nematic host with low-molar-mass dyes can significantly increase the orientational response of liquid crystal system (by two orders of magnitude at the dye concentration less than 1 wt% [5–10]). In dye-doped NLCs, the director can be rotated not only toward the light field but also perpendicular to it [6]. In the latter case, the refractive index of the extraordinary wave decreases and, correspondingly, an NLC exhibits a negative orientational nonlinearity. A specific phenomenon was

Address correspondence to M. P. Smayev, Lebedev Physical Institute, Leninsky pr. 53, 119991, Moscow, Russia. Tel.: +7-499-7833716; Fax: +7-499-1326833; E-mail: smayev@lebedev.ru

observed for NLCs doped with azodyes [7]: the nonlinearity sign of the dye-doped NLC depended on the angle between the director and the light field (sign-inversion nonlinearity). The mechanism of the dye-enhanced optical director reorientation is related to changing intermolecular forces under dye excitation.

High-molar-mass dopants are also attractive for inducing director reorientation in NLCs. It was found previously, that comb-shaped polymers induce orientational nonlinearity greater than that in the case of low-molar-mass azodyes similar in structure to photochromic groups of the polymers [9]. The nonlinearity sign of the polymer-doped NLC was negative, while the NLC doped with the azodye exhibited the sign-inversion nonlinearity.

Similar nonlinearity behavior was observed for the homodendrimer of the fifth generation and the azodye identical to dendrimer terminal fragments [11,12]. In [12], it was also found that the homodendrimer of the first generation induces sign-inversion nonlinearity. In [13], the light interaction with planar NLC doped with the second-generation carbosilane dendrimer with statistically distributed terminal aliphatic and azobenzene groups was studied. The orientational optical nonlinearity was found to be negative and the director field bistability was observed.

Below, we present the detailed comparative study of the orientational nonlinearity induced in NLCs by the carbosilane codendrimers of different (from the second to the fourth) generations.

2. Experimental

The study was performed with homeotropic and planar samples of nematic host ZhKM-1277 doped with carbosilane dendrimers. The dopant concentration was 0.15 wt%. The ZhKM-1277 material exhibits the nematic phase in the temperature range from -20°C to 60°C and has a positive dielectric anisotropy. Its refractive indices are $n_{\parallel} = 1.71$ and $n_{\perp} = 1.52$ at $\lambda = 589$ nm. The thickness of liquid crystal cells was 100 μm .

The dendrimers (Fig. 1) contain terminal aliphatic and mesogenic azobenzene fragments, which were statistically distributed over the dendritic surface. Dendrimers synthesis and properties are described in [14].

The absorption of the NLC cell was measured by an MS-122 spectrophotometer (PROSCAN Special Instruments). The data obtained indicate a sufficiently large dichroism of the dendrimer–NLC systems. For instance, in the case of the G4-doped NLC the absorption coefficients at the wavelength $\lambda = 473$ nm for the extraordinary and ordinary waves are $\alpha_{\parallel} = 20.1$ cm^{-1} and $\alpha_{\perp} = 10.4$ cm^{-1} , respectively.

We used the technique of aberrational self-phase modulation of the light beam [11,15]. The light source was a cw solid-state laser LCS-DTL-364 ($\lambda = 473$ nm). Linear polarization of the light beam could be rotated by a double Fresnel rhomb. The plane of liquid crystal layer was vertical; unperturbed NLC director was in the horizontal plane. The NLC cell could be rotated about the vertical axis to change the incidence angle α . The system of aberration rings was observed on the screen placed behind the cell.

The number N of the aberration rings is connected with the nonlinear phase shift ΔS_{NL} for the extraordinary wave as

$$N = |\Delta S_{\text{NL}}|/2\pi.$$

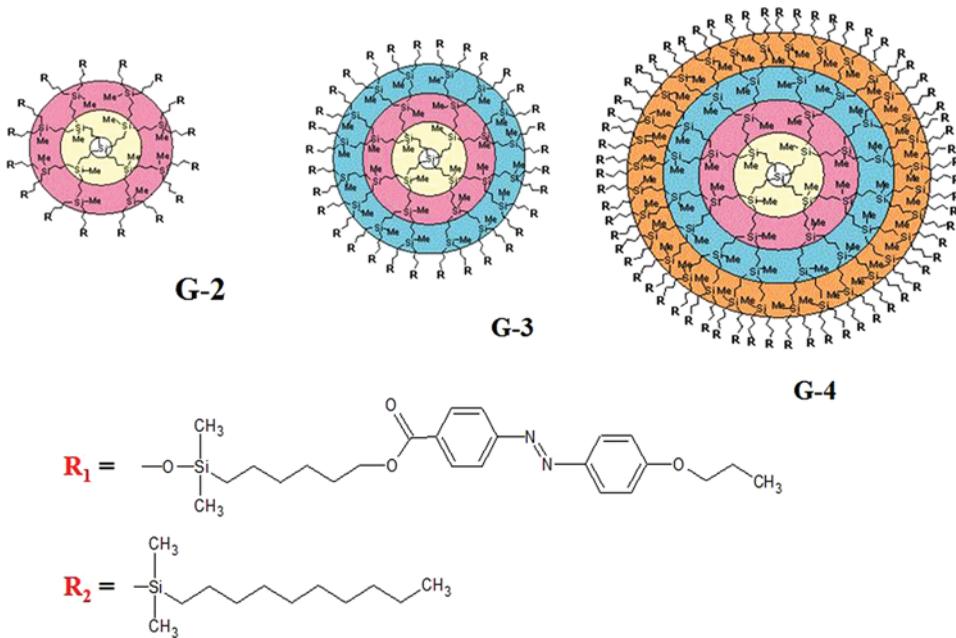


Figure 1. Carbosilane codendrimers of the second, third, and fourth generations. (Figure appears in color online.)

The phase shift ΔS_{NL} is expressed in terms of the change in the refractive index Δn for extraordinary wave averaged over the cell thickness

$$\Delta S_{NL} = 2\pi\Delta nL/\lambda,$$

where L is the cell thickness and λ is the wavelength. The sign of the light-induced refractive index (that is, the sense of the director rotation) was determined by the intensity redistribution in the aberration pattern at the rapid shift of the NLC cell upward relative to incident beam.

3. Results and Discussion

Illumination of all samples with the p-polarized light beam results in appearance of the aberration pattern of orientational nature, which was evidenced by the characteristic times of the pattern formation at oblique incidence and relaxation (~ 10 s).

For all samples and experimental geometries, we only observed the self-defocusing of the light beam, which implies that director rotates away from the light field (i.e. the nonlinearity is negative). Negative nonlinearity proves that the director reorientation is due to the presence of dendrimers, because the nonlinearity of undoped nematic host is always positive.

Dependences of the number N of the self-defocusing aberration rings and the magnitude of the averaged light-induced refractive index $|\Delta n|$ for a light beam obliquely incident on planar and homeotropic cells on the beam power P are shown in Figure 2. It is clearly seen that orientational response of liquid crystal system increases with the dendrimer generation number.

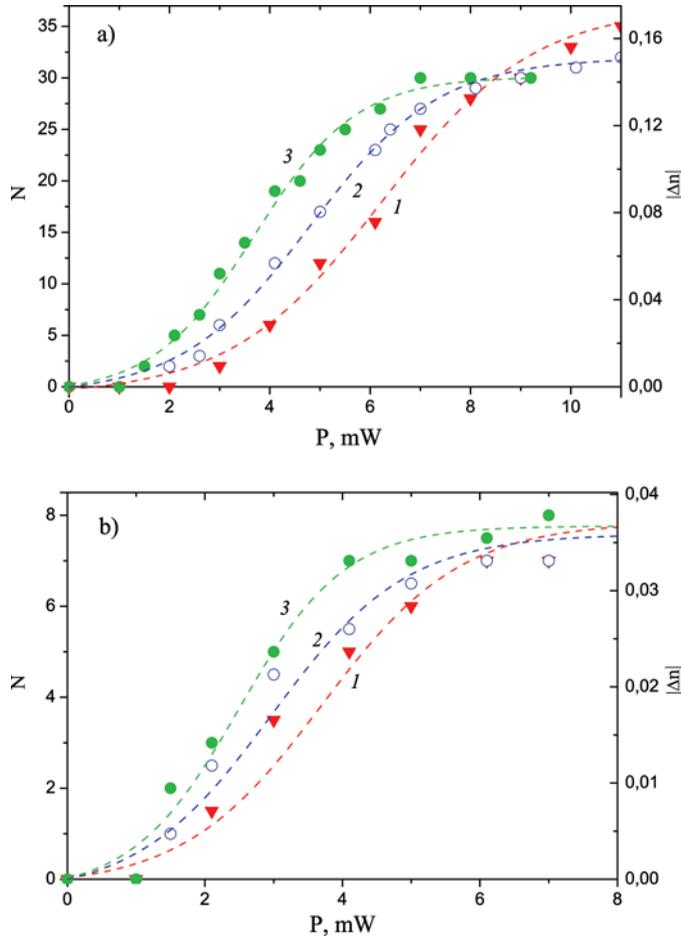


Figure 2. Dependences of the number N of the self-defocusing aberration rings and the magnitude of the averaged light-induced refractive index Δn for the light beam ($\lambda=473$ nm, $\alpha=50^\circ$) passed through (a) planar and (b) homeotropic NLCs doped with the dendrimers (1) G2, (2) G3, and (3) G4 on the light beam power P . (Figure appears in color online.)

We estimated the enhancement of the nonlinear optical response for planar NLC doped with G4 dendrimer. To this end, we determined the ratio of the light-beam powers at which an equal number of rings was observed for the homeotropic cell with pure host and the planar cell with the doped host and then divided it by the quantity $\alpha' = \alpha_{\parallel} + 2\alpha_{\perp}$ (which is proportional to the NLC absorptivity averaged over the director orientation). The calculated parameter $\eta_{\alpha} = -0.42$ cm (the minus sign indicates the negative nonlinearity) is smaller in magnitude than the parameter $\eta_{\alpha} = -2.3$ cm obtained for nematic host doped with comb-like polymer [9] and the value $\eta_{\alpha} = -0.94$ cm obtained for the homodendrimer of the fifth generation G5 (containing another azochromophore) [12].

Dependences of the aberration ring number and the magnitude of the light-induced refractive index on the direction of light-beam polarization are shown in Figure 3. It can be seen from this figure that polarization rotation from the p-polarization ($\varphi=0^\circ$) to the s-polarization ($\varphi=90^\circ$) leads to monotonic

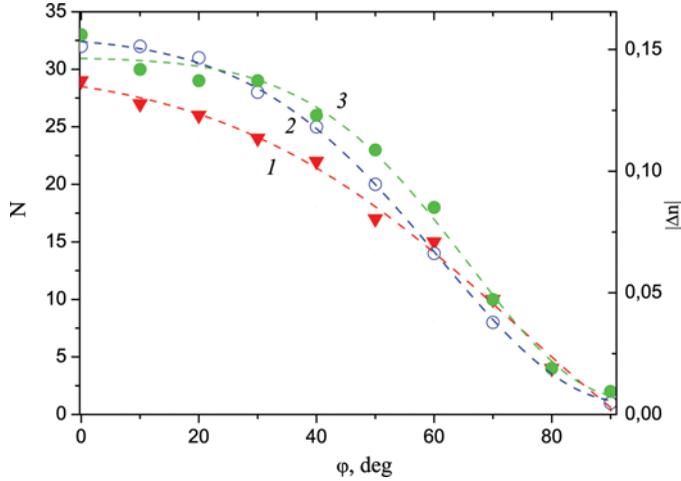


Figure 3. Dependences of the number N of the self-defocusing aberration rings and the magnitude of the averaged light-induced refractive index Δn on the angle φ of the light field polarization rotation ($\lambda = 473$ nm, $P = 8$ mW, $\alpha = 50^\circ$) for planar NLCs doped with 0.15 wt% of (1) G2, (2) G3, and (3) G4 dendrimers. Angle $\varphi = 0^\circ$ corresponds to the extraordinary wave; $\varphi = 90^\circ$, to the ordinary wave. (Figure appears in color online.)

suppression of the aberration pattern. Such behavior is characteristic of orientational nonlinearity in nematics and indicates the absence of significant thermal effects.

Application of external low-frequency voltage ($\nu = 3$ kHz) to homeotropic samples results in suppression of aberration rings due to elimination of light-induced director field inhomogeneity and reversion of NLC to the initial state. In the case of planar samples, the dependence is nonmonotonic (see Fig. 4 for the G3-doped

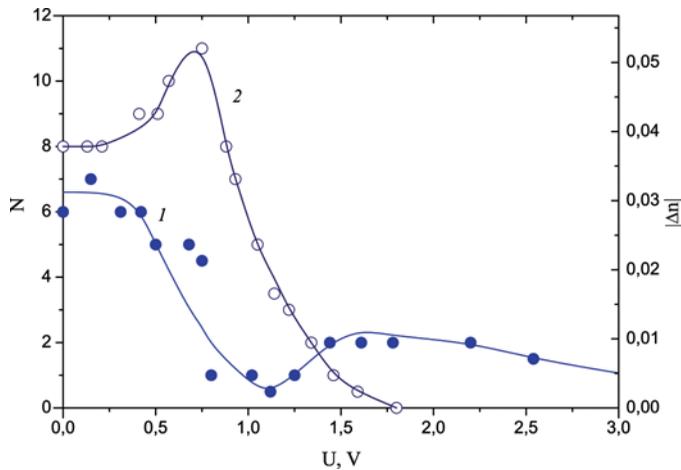


Figure 4. Dependences of the number N of the self-defocusing aberration rings and the magnitude of the averaged light-induced refractive index Δn on the applied low-frequency ($\nu = 3$ kHz) voltage U at illumination ($\lambda = 473$ nm, $P = 3$ mW) of planar ZhKM-1277 + 0.15% G3. Curve 1 corresponds to $\alpha = -50^\circ$; curve 2, to $\alpha = +50^\circ$. (Figure appears in color online.)

dopants the NLC director rotates away from the light field irrespective of the experimental geometry, i.e., the direction of the light propagation (relative to the director) and the light polarization. The complication of dendrimer structure (generation number) enhances the orientational optical response of the liquid crystal system. In particular, the light-induced Fredericksz transition threshold decreases by a factor of about 10 when passing from the second to the fourth generation. The width of bistability region (manifested at normal light incidence) decreases with the dendrimer generation number.

Acknowledgment

The authors are grateful to A.Yu. Bobrovsky and V.P. Shibaev for helpful discussions.

This study was supported by the Russian Foundation for Basic Research (projects no. 08-02-01382 and 09-02-12216), grant of the President of the Russian Federation (project no. MK-699.2009.2), the Program of Support for Young Scientists of the Presidium of the Russian Academy of Sciences (I.A.B and M.P.S), and the Federal Program "Scientific and Scientific-Pedagogical Personnel of Innovative Russia" (state contract no. 02.740.11.0447).

References

- [1] Zel'dovich, B. Ya., Pilipetskii, N. F., Sukhov, A. V., & Tabiryman, N. V. (1980). *JETP Lett.*, 31, 263.
- [2] Zolot'ko, A. S., Kitaeva, V. F., Kroo, N., Sobolev, N. N., & Chillag, L. (1980). *JETP Lett.*, 32, 158.
- [3] Khoo, I. C., & Zhuang, S. L. (1980). *Appl. Phys. Lett.*, 37, 3.
- [4] Tabiryman, N. V., Sukhov, A. V., & Zel'dovich, B. Ya. (1986). *Mol. Cryst. Liq. Cryst.*, 136, 1.
- [5] Janossy, I., Csillag, L., & Lloyd, A. D. (1991). *Phys. Rev. A*, 44, 8410.
- [6] Janossy, I., & Kosa, T. (1992). *Opt. Lett.*, 17, 1183.
- [7] Barnik, M. I., Zolot'ko, A. S., Romyantsev, V. G., & Terskov, D. B. (1995). *Crystallogr. Rep.*, 40, 691.
- [8] Marrucci, L., Paparo, D., Maddalena, P., Massera, E., Prudnikova, E., & Santamato, E. (1997). *J. Chem. Phys.*, 107, 9783.
- [9] Budagovsky, I. A., Zolot'ko, A. S., Ochkin, V. N., Smayev, M. P., Bobrovsky, A. Yu., Shibaev, V. P., & Barnik, M. I. (2008). *J. Expl Theor. Phys.*, 106, 172.
- [10] Khoo, I. C. (2009). *Phys. Rep.*, 471, 221.
- [11] Zolot'ko, A. S., Budagovsky, I. A., Ochkin, V. N., Smayev, M. P., Bobrovsky, A. Yu., Shibaev, V. P., Boiko, N. I., Lysachkov, A. I., & Barnik, M. I. (2008). *Mol. Cryst. Liq. Cryst.*, 488, 265.
- [12] Budagovsky, I. A., Ochkin, V. N., Smayev, M. P., Zolot'ko, A. S., Bobrovsky, A. Yu., Boiko, N. I., Lysachkov, A. I., Shibaev, V. P., & Barnik, M. I. (2009). *Liq. Cryst.*, 36, 101.
- [13] Babayan, E. A., Budagovsky, I. A., Zolot'ko, A. S., Smayev, M. P., Shvetsov, S. A., Boiko, N. I., & Barnik, M. I. (2010). *Bull. Lebedev Phys. Inst.*, 37, 257.
- [14] Lysachkov, A. I., Boiko, N. I., Rebrov, E. A., Muzafarov, A. M., & Shibaev, V. P. (2007). *Russ. Chem. Bull.*, 56, 2407.
- [15] Kitaeva, V. F., Zolot'ko, A. S., & Barnik, M. I. (2000). *Mol. Materials*, 12, 271.
- [16] Janossy, I., & Szabados, L. (1998). *Phys. Rev. E*, 58, 4598.